

Overdriven Characteristics of Silica Switching Devices

by Ary Syahriar

Submission date: 01-Nov-2020 04:01AM (UTC+0000)

Submission ID: 1432459049

File name: 6457-26642-1-PB.pdf (420.53K)

Word count: 2621

Character count: 14100

Overdriven Characteristics of Silica Switching Devices

2
2 Ary Syahriar¹, Nabil Rayhan Syahriar², Jusman Syafiie Djama³

^{1,3}Electrical Engineering Department, Faculty of Science and Technology University al Azhar Indonesia, Jakarta Indonesia

²Mechanical Engineering Department, Bandung Institute of Technology

*Corresponding author, e-mail: ary@uai.ac.id

Abstract

We have built and characterized silica on silicon switching devices fabricated by using the electron beam irradiation. It is based on Mach-Zehnder structure fabricated on silica on silicon layers where the upper cladding used the MgF₂ layers to bury the core. The switching speed of 2.0 μs has been achieved. To further increase the switching speed we have used larger voltage to the Ti heating electrode to increase the thermo optics effects on silica structures. The higher driving voltage have been used that falls to zero exactly as the first extinction is reached, therefore three fold increase in modulation speed is achieved.

Keywords: silica on silicon waveguides, switching devices, photonics devices, overdriven switching

1
Copyright © 2017 Universitas Ahmad Dahlan. All rights reserved.

1. Introduction

Optical waveguide switches are key component in modern optical communication networks. Many different optical switching technologies are currently available or under development. In practical use switching with stable and low driving power as well as polarisation insensitive are also necessary. These switching characteristics can be built using several effects such as: the electro-optic effect [1] [2], the thermo-optic (TO) effect [3]-[5], or mechanical means [6]. Recently, one of the leading technology for optical waveguide switching devices is Ti-diffusion in LiNbO₃, where the electro-optics effects have been used. Today, switched directional couplers based on LiNbO₃ devices are commercially available. However, it is polarization sensitive and expensive even though the main benefits of such devices can operate very fast, in the sub-nanosecond regime.

Polarisation insensitive in some applications is more important than high switching speed, such as switching in LAN with ring topologies and video distribution using circuit switching [8][19]. From those available technologies, the optical waveguide switching based on thermo-optics effects would be a good alternatives, because not only it offers polarisation independent effect it also gives switching times of the order of milliseconds.

The TO effects in material is the change of index refraction due to temperature changes. For optical waveguides the phase shifters usually consists of thin film heater deposited on top of the cladding layers of buried channel guides. In conventional TO phase shifters a thin film heater deposited on the cladding of a buried channel guide, usually the Ti heating electrode has been used. Since in a silica-on-silicon optical waveguide, the glass conductivity is larger than air, heat will be conducted to the silicon substrate, which acts as a heat sink. In the steady-state condition, the result is a linear temperature gradient between the heater and the substrate, which will rises the average temperature of the core. However, in this scheme relatively high power consumption is needed and lateral heat diffusion inside the glass may cause a thermal crosstalk between two closely spaced guides [9] [10]. These difficulties may be reduced by using a bridge-suspended waveguide or using etched groove waveguide structures, which can lowers the required drive power and reduces the thermal crosstalk [7]. However, switching time required is lengthened proportionally.

The main purpose of this article is to explain on thermo-optic switching using Mach-Zehnder interferometer (MZI) structures. A thermo optic phase shifter consisting of thin film heater deposited on top of one Mach-Zehnder arms has shown to be very effective to change

the effective refractive index of MZI so that the switching occurs. Further higher modulation speed can be achieved by increasing the driving voltage.

2. Research Method

The Mach-Zehnder interferometer (MZI) is another widely used device which has been developed to act as a switch (in its balanced form) and as a multiplexer or demultiplexer (in its balanced form) and it is a device that can use the TO effects excellently [11]. The MZI consists of two back to back Y-junctions, connected by linking waveguides. Introducing a phase delay to one linking guide via the thermo-optic effect enables the MZI to be used as a switching device as shown in Figure 1 (a). The phase shifter can be put in either or both of the straight arms to allow the relative phase of the recombining components to be altered [12][13]. If it is in the phase, the guided output is high and if it is out-of-phase, it is low.

When the phase shifter or heater is on, the waveguide temperature beneath the heater increases, then the effective optical straight arm length increases by $\left(\frac{dn}{dT}\right)L\Delta T$, here $\frac{dn}{dT}$ is the thermo-optic constant of the silica waveguide, L is the heater length and ΔT is the temperature rise [17]. The typical value of $\frac{dn}{dT}$ for silica is $10^{-5}^{\circ}\text{C}^{-1}$. For example, heating a 10 mm long guide by 15.23°C will produce a π radians phase shift at $1.523\text{ }\mu\text{m}$ wavelength [14]. The power needed and the response time are heavily depend on the thickness of cladding layer, thermal conductivity of silica waveguides and the lower substrate material used. In the case of silica on silicon structure, where the heat supplied by the Ti heater diffuses into the lower Si substrate through the MgF_2 cladding layers immediately below the heater and then through SiO_2 layer immediately beneath the MgF_2 . This immediate heat diffusion between the three material layers due to the thermal conductivity of Si is much larger than that of SiO_2 , MgF_2 and the surrounding air. Any lateral heat flow into the cladding glass is small, and all the glass reaches thermal equilibrium very quickly [15][17].

The characteristics of output power of Mach-Zehnder interferometers can easily be described by using the coupled mode theory. In the simplest case, assuming no loss and perfect y-branches with a 3-dB splitting ratio, the output power is given by [16][18]:

$$P_{out} = P_{in} \cos^2\left(\frac{\varphi}{2}\right) \quad (1)$$

where P_{out} and P_{in} are the optical output and input powers respectively, and φ is the phase difference between the two paths. A phase difference may be changed by changing the refractive index of one arm with respect to the other. If the change in refractive index is proportional to the temperature change, it must also be proportional to the power dissipated in the heater, so the output intensity is given by:

$$P_{out} = P_{in} \cos^2\left(\frac{\pi P}{2 P_{\pi}}\right) \quad (2)$$

where $P = \frac{V^2}{R}$ is the electric power dissipated in the heater, V is the applied voltage, R is the measured heater resistance, and P_{π} is the power which gives a π radians phase shift.

The structure of the Mach-Zehnder Interferometers 1x1 single mode optical switches used to investigate thermo-optic switching in irradiated waveguides is shown in Figure 1. The device has two straight arms of 10 mm length and an additional thin film of Ti metal, to act as a heater electrode.

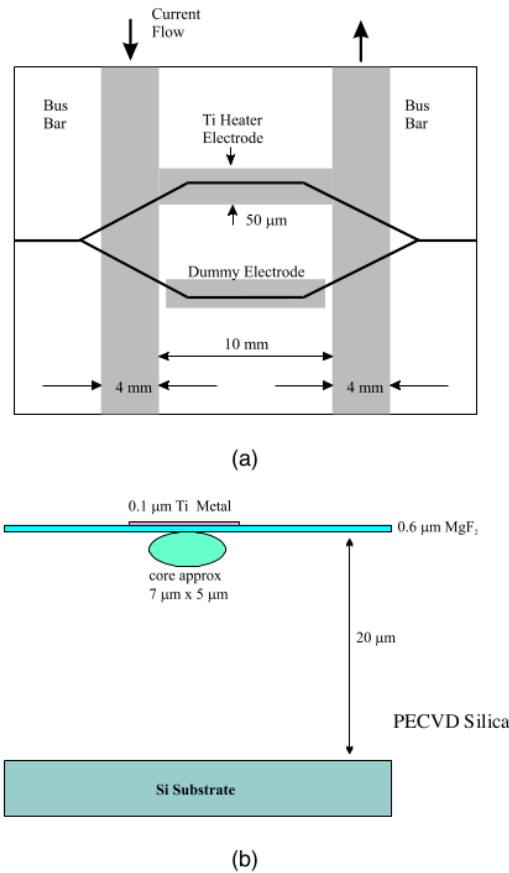


Figure 1. (a) Layout of thermo-optic Mach-Zehnder interferometric switches, (b) Cross section of a straight guide of a Mach-Zehnder interferometer with an MgF_2 cladding layer and an additional Ti heater

The waveguides were formed in PECVD silica-on-silicon. Irradiation parameters of 1.06 cm^2 charge dose at 30 keV energy were chosen to obtain essentially polarization independent insertion losses of 7–1 dB at $\lambda=1.523 \mu\text{m}$ for 3.4 cm lengths of straight guide with an oil cladding. The guide width was 7 μm , and the index difference between the core and buffer layer was $\Delta n \approx 6 \times 10^{-3}$. Insertion losses for an electrodeless interferometer measured using an oil cladding were 2.0 dB (TE) and 2.5 dB (TM), with the difference being ascribed to slight birefringence. The heater was deposited above one arm of each interferometer by patterning a 0.1 μm thick layer of sputtered Ti metal into 50 μm wide strips fed by 4 mm wide bus bars, and a dummy electrode was placed above the unheated arm to avoid any phase or amplitude imbalance [14].

The current for the heater was supplied by a signal generator. However, due to the very low maximum voltage (10 V) provided by the source, a high power driving circuit was needed. Figure 2 shows the driver used in the experiments. It consists of two transistors (TR1 and TR2), which are used as a power switches. A minimum driving voltage of 0.7 V turns on the transistor TR1 which in turn switches transistor TR2 on and off allowing the supply voltage of +V to be dropped across the heater. With a suitable DC supply, this circuit provides a maximum output of up to 65 V [14].

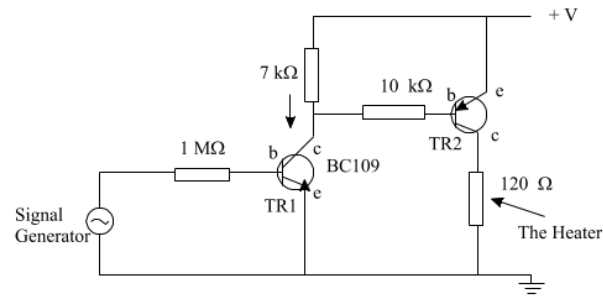


Figure 2. Driver circuit used to control the Ti heater

3. Results and Analysis

The measurement of switching characteristics was performed using a laser at a wavelength of $1.523 \mu\text{m}$. The incident light was butt-coupled into the input end facet of the device using a single mode fibre. The circuit of Figure 2 was used to supply current to the heater and hence obtain a phase shift. The output light was detected using a photodetector, and the time variation of the detected signal was displayed on an oscilloscope.

Three types of experiment were carried out. In the first experiment, the variation of transmission with heater power was measured by applying a low frequency square-wave voltage of varying amplitude to the heater. In the second, faster-varying signals were used and the frequency response of the switch was measured. In the third, overdriven switching characteristics were measured. Figure 3 shows the variation of normalised transmission with heater power, which follows the conventional sinusoidal form. Points are experimental data; the solid line represents the calculated transmission as given by a best fit to Equation (2). Switching performance was essentially similar to devices demonstrated by other technologies [3] [15]. The lack of phase bias in the curve suggests that there is no phase shift between the two-interferometer arms, although the relatively poor extinction ratio (10 dB) suggests unequal splitting in the Y-junctions. The first extinction was obtained at a power of $\approx 0.5 \text{ W}$ while the second was obtained at a power of $\approx 1.6 \text{ W}$.


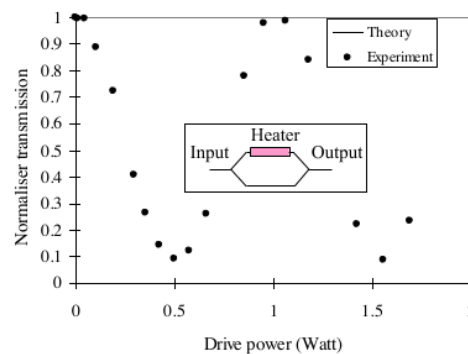



Figure 3. Variation of normalized transmission with heater power for a thermo-optic Mach-Zehnder interferometer modulator formed by irradiation

Figures 4 (a), (b), (c) show switch characteristics obtained using a square wave heater drive at frequencies of 125 Hz, 500 Hz and 1 kHz, respectively. Complete switching is clearly achieved at the lowest frequency. However, as the drive frequency is raised, the relatively slow


response of the switch quickly limit its ability to reach the ON and OFF states fully. Minimum switching times of ≈ 0.5 ms are slightly shorter than results obtained with topographic guides with a much thicker silica cladding, formed by flame hydrolysis deposition [17].

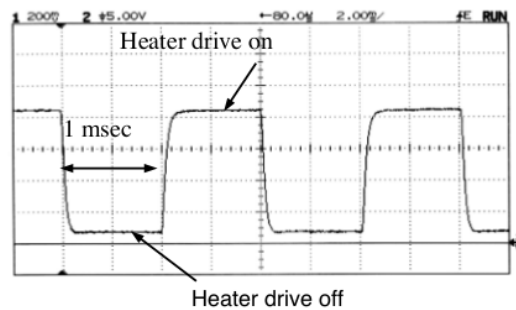

(a)

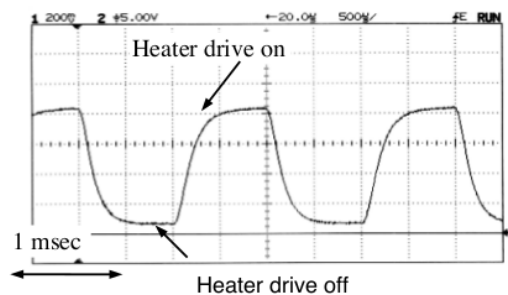

(b)

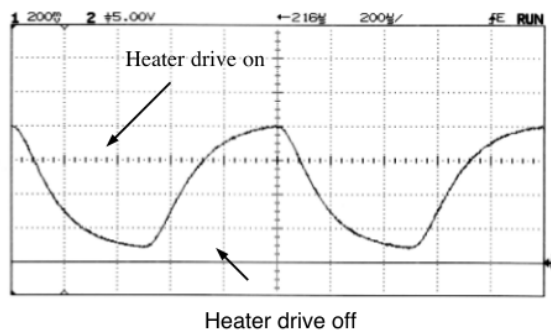

(c)

Figure 4 (a). Mach-Zehnder Interferometer switching characteristics obtained using a square wave heater drive at (a) 125 Hz, (b) 500 Hz, (c) 1 kHz.

In the previous set of experiments, the switch was driven using a voltage exactly sufficient to reach the first extinction. Faster switching speeds can in fact be achieved by using larger driving voltages. For example, Figure 5 (a) shows the switch characteristic obtained using a square wave of voltage 64 V at a frequency of 125 Hz. Here, the heater power is sufficient to

drive the switch past the first extinction, through the following maximum, and then to the second extinction. Due to the increased drive power, the first extinction is reached extremely rapidly. Figure 5 (b) shows the corresponding trace obtained at 3 kHz.

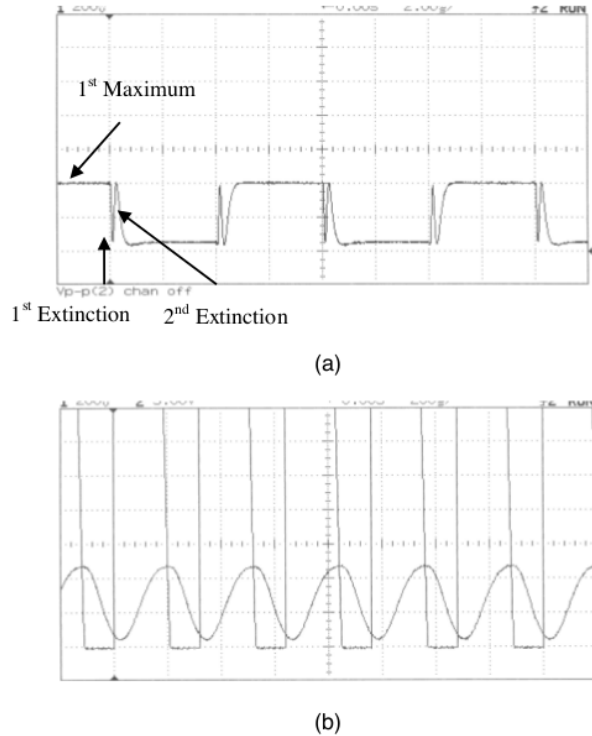


Figure 5. Overdriven switch characteristic obtained using a square wave heater drive with a voltage of 64 V and a frequency of (a) 125 Hz, (b) 3 kHz.

In this case, the drive signal falls to zero exactly as the first extinction is reached, allowing an approximately three-fold increase in modulation speed over the corresponding result shown in Figure 3 (c). A periodic switching at similar speed may be obtained using shaped drive pulse, where an initially large switching voltage is followed by a smaller holding voltage.

4. Conclusions

We have characterized the switching devices based on Mach ⁵hnder interferometer where thin layers of evaporated MgF_2 can be used as a cladding for waveguides formed by electron beam irradiation of PECVD silica-on-silicon. Switching can be realized by using a thin film heater to induce refractive index changes in waveguide structures. An unequal splitting in the Y-junctions results in poor extinction, however, a major disadvantage. Switches based on directional couplers would be a good alternative, but heating one waveguide without affecting the other in such a closely-spaced geometry is extremely difficult.

References

- [1] HS Hinton. Photonic switching using directional couplers. *IEEE Communication Mag.* 1987; 25: 16-26.

- [2] O Mitomi, H Miyazawa, K Noguchi. Waveguide-type LiNbO₃ high-speed optical switches. *NTT Review*. 1995; 7: 35-40.
- [3] M Haruna, J Koyama. Thermo-optic deflection and switching in glass. *Appl. Opt.* 1982; 21: 3461-3465.
- [4] M Haruna. Thermo-optic waveguide devices. *JARECT Optical Devices & Fibers*. 1985; 17: 69-81.
- [5] M Haruna, J Koyama. *Thermo-optic waveguide interferometric modulator/switch in glass*. IEE Proceedings Pt. H. 1984; 131: 322-324.
- [6] E Ollier, P Lebeye, F Revol. Micro-opto mechanical switch integrated on silicon. *Elect. Lett.* 1995; 31: 2003-2005.
- [7] A Sugita, K Jinguiji, N Takato, K Katoh, M Kawachi. Bridge-suspended silica-waveguide thermo-optic phase shifter and its application to Mach-Zehnder type optical switch. *IEICE Trans. Electron.* 1990; E-73: 105-109.
- [8] WK Ritchie. Overview of local access development. *BT. Tech. J.* 1989; 7: 7-16.
- [9] T Aoki, Y Nishimura. Technical trends on electromechanical devices. *IEICE Trans. Electron.* 1994; E77-C: 1536-1544.
- [10] Y Inoue, K Katoh, M Kawachi. Polarization sensitivity of a silica waveguide thermo-optic phase shifter for planar lightwave circuit. *IEEE Photon.Lett.* 1992; 4: 36-38.
- [11] M Okuno, A Sugita, T Matsunaga, M Kawachi, Y Ohmori, K Katoh. 8x8 optical matrix switch using silica-based planar lightwave circuit. *IEICE Trans. Electron.* 1993; E76-C, 1215-1223.
- [12] Y Hida, H Onose, S Imamura. Polymer waveguide thermo-optic switch with low electric power consumption at 1.3 μm . *IEEE Photon.Lett.* 1993; 5: 782-784.
- [13] MBJ Diemeer, JJ Brons, ES Trommel. Polymeric optical waveguide switch using the thermo-optic effect. *IEEE J. Lightwave Technol.* 1989; LT-7: 449-453.
- [14] A Syahriar, RRA Syms, TJ Tate. Thermo-optic interferometric switches fabricated by electron beam irradiation of silica-on-silicon. *IEEE J. Lightwave Technol.* 1998; LT-16: 841-846.
- [15] HM Presby, CA Edwards. Packaging of glass waveguide silicon devices. *Opt. Engng.* 1992; 31: 141-143.
- [16] RRA Syms, TJ Tate, JJ Lewandowski. Near-infrared channel waveguides formed by electron-beam irradiation of silica layers on silicon substrates. *IEEE J. Lightwave Technol.* 1994; LT-12: 2085-2091.
- [17] M Kawachi. Silica waveguide on silicon and their application to integrated optic components. *Opt. Quant. Elect.* 1990; 22: 391-416.
- [18] N Takato, K Jinguiji, M Yasu, H Toba, M Kawachi. Silica-based single-mode waveguides on silicon and their application to guided-wave optical interferometers. *IEEE J. Lightwave Technol.* 1988; LT-6: 1003-1010.

Overdriven Characteristics of Silica Switching Devices

ORIGINALITY REPORT

11%

SIMILARITY INDEX

5%

INTERNET SOURCES

8%

PUBLICATIONS

3%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|---|----|
| 1 | journal.uad.ac.id
Internet Source | 2% |
| 2 | Ary Syahriar, Nabil Rayhan Syahriar, Jusman Syafii Djamal, Randy Rahmat Saleh. "A General S-bend Approximation by Cascading Multiple Sections of Uniformly Curved Waveguides", Journal of Physics: Conference Series, 2019
Publication | 1% |
| 3 | Adam Densmore. "Compact and low power thermo-optic switch using folded silicon waveguides", Optics Express, 06/22/2009
Publication | 1% |
| 4 | Submitted to Padjadjaran University
Student Paper | 1% |
| 5 | repository.ntu.edu.sg
Internet Source | 1% |
| 6 | Submitted to Universitas Brawijaya
Student Paper | 1% |
| 7 | R. Kasahara. "Low-power consumption silica- | |

based 2×2 thermooptic switch using trenched silicon substrate", IEEE Photonics Technology Letters, 1999

Publication

1 %

8

R.R.A. Syms, T.J. Tate, J.J. Lewandowski. "Near-infrared channel waveguides formed by electron-beam irradiation of silica layers on silicon substrates", Journal of Lightwave Technology, 1994

Publication

1 %

9

Y HIBINO. "PLC-type Thermooptic Switches for Photonic Networks", WDM Technologies, 2003

Publication

<1 %

10

B. Jalali. "Advances in silicon-on-insulator optoelectronics", IEEE Journal of Selected Topics in Quantum Electronics, 1998

Publication

<1 %

11

Orignac, Xavier, Jan Ingenhoff, Norbert Fabricius, and S. Iraj Najafi. "", Integrated Optics Devices III, 1999.

Publication

<1 %

12

cumsl.msl.columbia.edu

Internet Source

<1 %

13

R. Kasahara, M. Yanagisawa, T. Goh, A. Sugita, A. Himeno, M. Yasu, S. Matsui. "New structure of silica-based planar lightwave circuits for low-power thermooptic switch and its application to 8

<1 %

× 8 optical matrix switch", Journal of Lightwave Technology, 2002

Publication

14

M. Okuno, K. Kato, Y. Ohmori, M. Kawachi, T. Matsunaga. "Improved 8×8 integrated optical matrix switch using silica-based planar lightwave circuits", Journal of Lightwave Technology, 1994

Publication

<1%

15

Advances in Integrated Optics, 1994.

Publication

<1%

Exclude quotes On

Exclude matches Off

Exclude bibliography On